

UNCLASSIFIED

AD NUMBER

AD876393

LIMITATION CHANGES

TO:

Approved for public release; distribution is unlimited. Document partially illegible.

FROM:

Distribution authorized to U.S. Gov't. agencies and their contractors; Critical Technology; SEP 1970. Other requests shall be referred to Office of Naval Research, Arlington, VA 22217. This document contains export-controlled technical data.

AUTHORITY

onr ltr, 13 jan 1972

THIS PAGE IS UNCLASSIFIED

HPC 70-119

MONSANTO/WASHINGTON UNIVERSITY
ONR/ARPA ASSOCIATION

20
On

**CALCULATION OF STRESS - STRAIN CURVES FROM RELAXATION
DATA IN THE RUBBERY - FLOW REGION**

BY
M. NARKIS

This document is subject to special export controls and each transmittal to foreign governments or foreign nationals may be made only with prior approval of the Director of Material Sciences, Office of Naval Research.

Washington, Va., 22217

PROGRAM MANAGER
ROLF BUCKDAHL

MONSANTO RESEARCH CORPORATION

A SUBSIDIARY OF MONSANTO COMPANY

800 N. LINDBERGH BOULEVARD

ST. LOUIS, MISSOURI 63166



ACCESSION	
CFSTI	SECTION <input type="checkbox"/>
DDC	SECTION <input checked="" type="checkbox"/>
UNCLASSIFIED	<input type="checkbox"/>
JOS	
BY	
DISTR. AC. FOR AVAILABILITY CODES	
DIST.	AVAIL. DDC, OR SPECIAL
2	

NOTICES

When Government drawings, specifications, or other data are used for any purpose other than in connection with a definitely related Government procurement operation, the United States Government thereby incurs no responsibility nor any obligation whatsoever; and the fact that the Government may have formulated, furnished, or in any way supplied the said drawings, specifications, or other data, is not to be regarded by implication or otherwise as in any manner licensing the holder or any other person or corporation, or conveying any rights or permission to manufacture, use, or sell any patented invention that may in any way be related thereto.

DDC release to CFSTI is not authorized.

HPC 70-119

CALCULATION OF STRESS - STRAIN CURVES FROM RELAXATION
DATA IN THE RUBBERY - FLOW REGION

BY

M. NARKIS
MATERIALS RESEARCH LABORATORY
WASHINGTON UNIVERSITY

SEPTEMBER 1970

MONSANTO/WASHINGTON UNIVERSITY ASSOCIATION
HIGH PERFORMANCE COMPOSITES PROGRAM
SPONSORED BY ONR AND ARPA
CONTRACT NO. N00014-67-C-0218, ARPA ORDER 876
ROLF BUCHDAHL, PROGRAM MANAGER

MONSANTO RESEARCH CORPORATION
800 NORTH LINDBERGH BOULEVARD
ST. LOUIS, MISSOURI 63166

FOREWORD

The research reported herein was conducted by the staff of the Monsanto/Washington University Association under the sponsorship of the Advanced Research Projects Agency, Department of Defense, through a contract with the Office of Naval Research, N00014-67-C-0218 (formerly N00014-66-C-0045), ARPA Order No. 876, ONR contract authority NR 356-484/4-13-66, entitled "Development of High Performance Composites."

The prime contractor is Monsanto Research Corporation. The Program Manager is Dr. Rolf Buchdahl. (Phone: Area Code 314-694-4721).

The contract is funded for 6,000,000 and expires 30 April 1971.

CALCULATION OF STRESS - STRAIN CURVES FROM RELAXATION
DATA IN THE RUBBERY - FLOW REGION

M. Narkis*
Materials Research Laboratory
Washington University
St. Louis, Missouri 63130

ABSTRACT

Stress relaxation curves for polysulfone and Lexan polycarbonate are only time dependent at a constant temperature if strain is defined as $\epsilon_H = \ln (l/l_0)$ and the "true" cross-sectional area $A = A_0/(1 + \epsilon)$ is used. The strain independent stress relaxation curves can be used to calculate stress-strain curves at different rates of strain according to the linear viscoelastic theory. The agreement between experimental and calculated stress-strain curves is good at least up to about 60% strain in the range of 0.01 to 0.2 in/min rate of extension if an average rate of strain defined by $\bar{\epsilon}_H = 1/t \ln (l/l_0)$ is used.

*Presently with the Center for Industrial Research, POB 311, Haifa, Israel.

(Contribution HPC 70-119 from the Monsanto/Washington University Association sponsored by the Advanced Research Projects Agency, Department of Defense, under Office of Naval Research Contract No. N00014-67-C-0218.)

CALCULATION OF STRESS - STRAIN CURVES FROM RELAXATION DATA IN THE RUBBERY-FLOW REGION

M. Narkis
Materials Research Laboratory
Washington University
St. Louis, Missouri 63130

Introduction

A linear viscoelastic body, Maxwell-Wiechert body [1], under a constant rate of strain $\dot{\epsilon}$ is described by the following equation:

$$f(t) = \dot{\epsilon} \int_{-\infty}^{\infty} \tau H(\tau) (1 - e^{-t/\tau}) d \ln \tau \quad (1)$$

where $f(t)$ is the stress at time t , τ is the relaxation time which varies between zero and infinity, and $H(\tau)$ is the distribution of relaxation times. Differentiation of Equation (1) with respect to time yields [2, 3, 4],

$$\frac{df(t)}{dt} = \dot{\epsilon} \int_{-\infty}^{\infty} H(\tau) e^{-t/\tau} d \ln \tau = \dot{\epsilon} E_r(t) \quad (2)$$

or

$$f(t) = \dot{\epsilon} \int_0^t E_r(t) dt = \dot{\epsilon} \int_{-\infty}^{\ln t} t E_r(t) d \ln t \quad (3)$$

Another form of equation (2) was given by Smith [5],

$$E_r(t) = F(t) \left[1 + \frac{d \log F(t)}{d \log t} \right] \quad (4)$$

where $F(t) = f(t)/\dot{\epsilon}t$ and $E_r(t)$ is the relaxation modulus. Smith studied Equation (4) by analyzing experimental data on NBS polyisobutylene and SBR elastomer.

Tensile measurements carried out by using the Instron machine are done under constant extension rate. If the instantaneous rate of strain is defined by $\dot{\epsilon} = 1/L \cdot dL/dt$, the strain ϵ_H (Hencky strain) and the average rate of strain $\bar{\epsilon}_H$, when the sample is extended from L_0 ($t = 0$) to L in a time interval $\Delta t = t$, are given by $\epsilon_H = \ln(L/L_0)$ and $\bar{\epsilon}_H = 1/t \ln(L/L_0)$ respectively.

The logarithmic definition of strain was found appropriate for the experimental data shown in this paper, this strain definition was also recently used by Vinogradov et al. [6] for polystyrene at 130°C. Ballman [7] studied the stress-strain curves of polystyrene at 300°F and at different rates of strain. The rate of strain $d \ln(L/L_0)/dt$ in his experiments was kept constant. The cross-sectional area A decreases with the extension and assuming a constant volume then $A = A_0/(1 + \epsilon)$ where A_0 is the initial cross-section area and $\epsilon = \Delta L/L_0$.

Equation (3) is applied to the experimental data as follows:

$$f(t) = (1 + \epsilon) f_0(t) = \ln(L/L_0)/t \int_{-\infty}^{Lnt} t E_r(t) dLnt \quad (5)$$

where $f_0(t)$ is the stress calculated on the initial cross-section area. The cross-section area correction and the logarithmic strain were also applied to the stress relaxation data.

EXPERIMENTAL

Stress relaxation and stress-strain data were obtained for polysulfone (1700 Union Carbide) and Lexan polycarbonate ($\bar{M}_w = 29,000$, General Electric). Sheets of polysulfone and polycarbonate were compression molded and strips, about 0.1 in. thick and 0.75 in. wide, were cut from them. The distance between the grips was 3 in.

In stress relaxation experiments samples were extended at 2 in/min to a certain elongation and force-time curves were recorded. Force-elongation curves were studied at three rates of extension, namely, 0.01, 0.05 and 0.2 in/min.

Stress relaxation curves were obtained at several temperatures and shifted to 187°C and 160°C for the polysulfone and polycarbonate, respectively. Stress-strain curves were studied at 187°C and 160°C for the polysulfone and polycarbonate, respectively.

At least two samples were tested in each case.

RESULTS AND DISCUSSION

A relaxation curve which is time dependent at a constant temperature and does not depend on strain can be converted into stress-strain data by using Equation (5). The dependence of the relaxation modulus upon strain was studied at four different strains. Results for polysulfone are shown in Figure 1 where four stress relaxation curves are plotted at 5, 10, 20 and 40% strain, the effect of strain on these curves is very significant. In figure 1 a stress relaxation curve, where $E_r(t)$ is calculated on the "true" cross-section area and the Hencky strain is used, is also shown. In this case, the stress relaxation curve is practically independent of strain at least up to 40%. Similar results were found for the Lexan polycarbonate and the strain

independent stress relaxation curves were used for further calculation of stress-strain curves with the aid of Equation (5). The possibility of separation of time and strain dependence of the stress for other polymers was shown by other researchers [5,8].

The range of rates of extension that was studied is 0.01 to 0.2 in/min. Experimental and calculated stress-strain curves for the polysulfone are shown in Figure 2. At very slow rates of extension the experiment extends to long times and since high temperatures are involved the stability of the polysulfone becomes an important factor and especially in experiments that are carried out under air. Shifted stress relaxation data from lower temperatures become more important for calculated stress-strain curves at higher rates of extension, thus, the additional error due to shifting results in predicted stress-strain curves that are less accurate. Figure 2 shows that in the range of 0.01 to 0.2 in/min., the agreement between calculated curves and experimental data is good.

In Figure 3 stress relaxation curves at three different temperatures are shown for Lexan polycarbonate ($\overline{M}_w = 29,000$). The curves for 154 and 170°C were shifted to the 160°C curve. By using the shift factors and a modified WLF equation for polycarbonate given by Tobolsky, et. al. [9] a value of $T_i = 147^\circ\text{C}$ was obtained. T_i values of 150 and 155°C for 40,000 and 90,000 molecular weight Lexan polycarbonate, respectively, were given by Tobolsky, et. al. In Figure 3, the 160°C relaxation curve is also represented by plotting $t E_r(t)$ versus $\log t$, thus the value of the integral in Equation (5) can be graphically obtained.

Stress-strain behavior was studied at 160°C at three different constant extension rate experiments. The data are shown in Figure 4 and compared with calculated curves.

Figure 4 shows that stress-strain curves for the Lexan polycarbonate can be predicted from relaxation data with reasonable accuracy at least up to strain of 60%. Tobolsky, et. al, [9] , by measuring the relaxation curve at three different strains, have shown that practically for Lexan polymer ($\overline{M}_w = 40,000$) $E_r(t)$ does not depend on strain at least up to 25% elongation.

If the "true" experimental tensile stress is divided by the integral term in Equation (3), the value of $\dot{\epsilon}$ is obtained. Table I shows that $\dot{\epsilon}$ decreases with time as $\overline{\epsilon}$ does. One of the major reasons for this behavior can be attributed to the non-constant rate of strain experiments under constant extension rates, where high strains are involved.

In summary, stress relaxation data on a polysulfone and Lexan polycarbonate are appropriate for calculation of their stress-strain behavior in the rubbery-flow regions, according to the linear viscoelastic theory and by using proper definitions of strain and rate of strain and correcting for the cross-section area change with strain.

Acknowledgment

This work was sponsored by the Advanced Research Projects Agency, Department of Defense and Office of Naval Research under Contract No. N00014-67-C-0218 (formerly N00014-66-C-0045).

REFERENCES

1. A. V. Tobolsky, Structure and Properties of Polymers, Wiley, New York, 1960, p. 107.
2. R. Sips, J. Polymer Science, 5, 69, (1950).
3. J. D. Ferry, Viscoelastic Properties of Polymers, Wiley, New York, 1961, p. 431.
4. A. V. Tobolsky and L. L. Chapoy, Journal of Polymer Science, 6B, 493 (1968).
5. T. L. Smith, Trans. Soc. Rheol., 6, 61 (1962).
6. G. V. Vinogradov, D. D. Fikhman, B. V. Radushkevitch and A. Ya. Malkin, Journal of Polymer Science, Part A-2, 8, 657 (1970).
7. R. L. Ballman, Rheologica Acta, 4, 137 (1965).
8. R. D. Andrews, N. Hofman - Bang and A. V. Tobolsky, J. Polymer Science, 3, 669 (1948).
9. J. P. Mercier, J. J. Aklonis, M. Litt and A. V. Tobolsky, J. Appl. Polymer Science, 9, 447 (1965).

TABLE I. COMPARISON OF $\dot{\epsilon}$ CALCULATED BY USING STRESS-STRAIN AND RELAXATION DATA, WITH $\bar{\epsilon} = \ell_n (\ell/\ell_0)$

t min	$\int_0^t E_r(t)dt$ $\times 10^{-9}$ $\frac{\text{dyne}\cdot\text{sec}}{\text{cm}^2}$	0.2 in/min			0.05 in/min			0.01 in/min		
		f(t)			f(t)			f(t)		
		$\times 10^{-6}$	$\dot{\epsilon} \times 10^3$	$\bar{\epsilon} \times 10^3$	$\times 10^{-6}$	$\dot{\epsilon} \times 10^4$	$\bar{\epsilon} \times 10^4$	$\times 10^{-6}$	$\dot{\epsilon} \times 10^5$	$\bar{\epsilon} \times 10^5$
		$\frac{\text{dyne}}{\text{cm}^2}$	$\frac{1}{\text{sec}}$	$\frac{1}{\text{sec}}$	$\frac{\text{dyne}}{\text{cm}^2}$	$\frac{1}{\text{sec}}$	$\frac{1}{\text{sec}}$	$\frac{\text{dyne}}{\text{cm}^2}$	$\frac{1}{\text{sec}}$	$\frac{1}{\text{sec}}$
1	3.25	3.6	1.10	0.97	0.83	2.55	2.46	-	-	-
2	5.40	5.7	1.05	0.95	1.39	2.57	2.46	-	-	-
5	10.7	10.1	0.94	0.87	2.74	2.56	2.41	0.60	5.60	5.1
10	17.6	14.5	0.82	0.77	4.15	2.35	2.32	0.99	5.65	5.1
20	29.6	-	-	-	6.00	2.03	2.20	1.57	5.30	5.0
40	43.5	-	-	-	7.40	1.70	1.95	2.35	5.40	4.8
60	58.5	-	-	-	-	-	-	2.94	5.03	4.7
80	70.0	-	-	-	-	-	-	3.40	4.85	4.6
125	86.0	-	-	-	-	-	-	3.82	4.45	4.35

LIST OF FIGURES

Figure 1. Stress relaxation curves, $E(t)$ at various strains and strain independent curve, $E_r(t)$. polysulfone, 187°C.

Figure 2. Stress-strain curves at various rates of extension. polysulfone, 187°C.
_____ experimental. -----calculated.

Figure 3. Relaxation curves at different temperatures for Lexan polycarbonate.

Figure 4. Stress-strain curves at various rates of extension. Lexan polycarbonate, 160°C. _____ experimental. -----calculated.


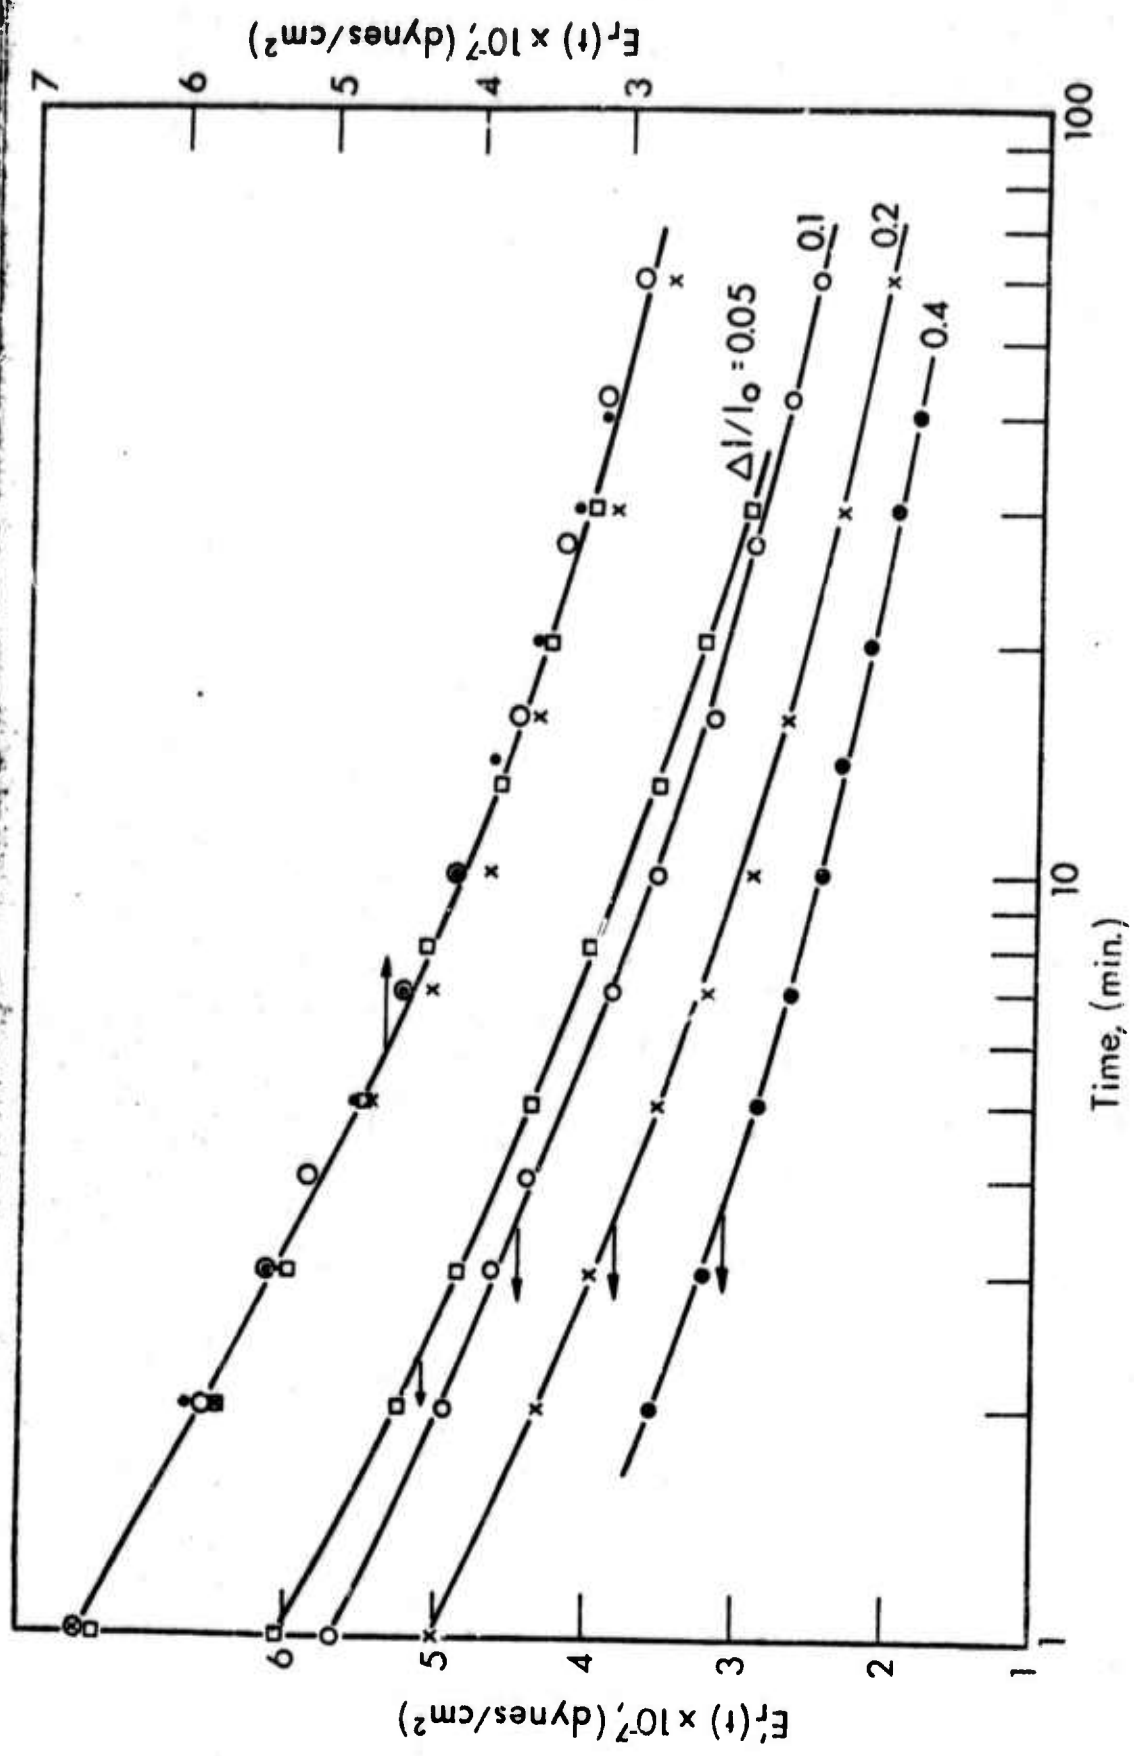


Fig. 1

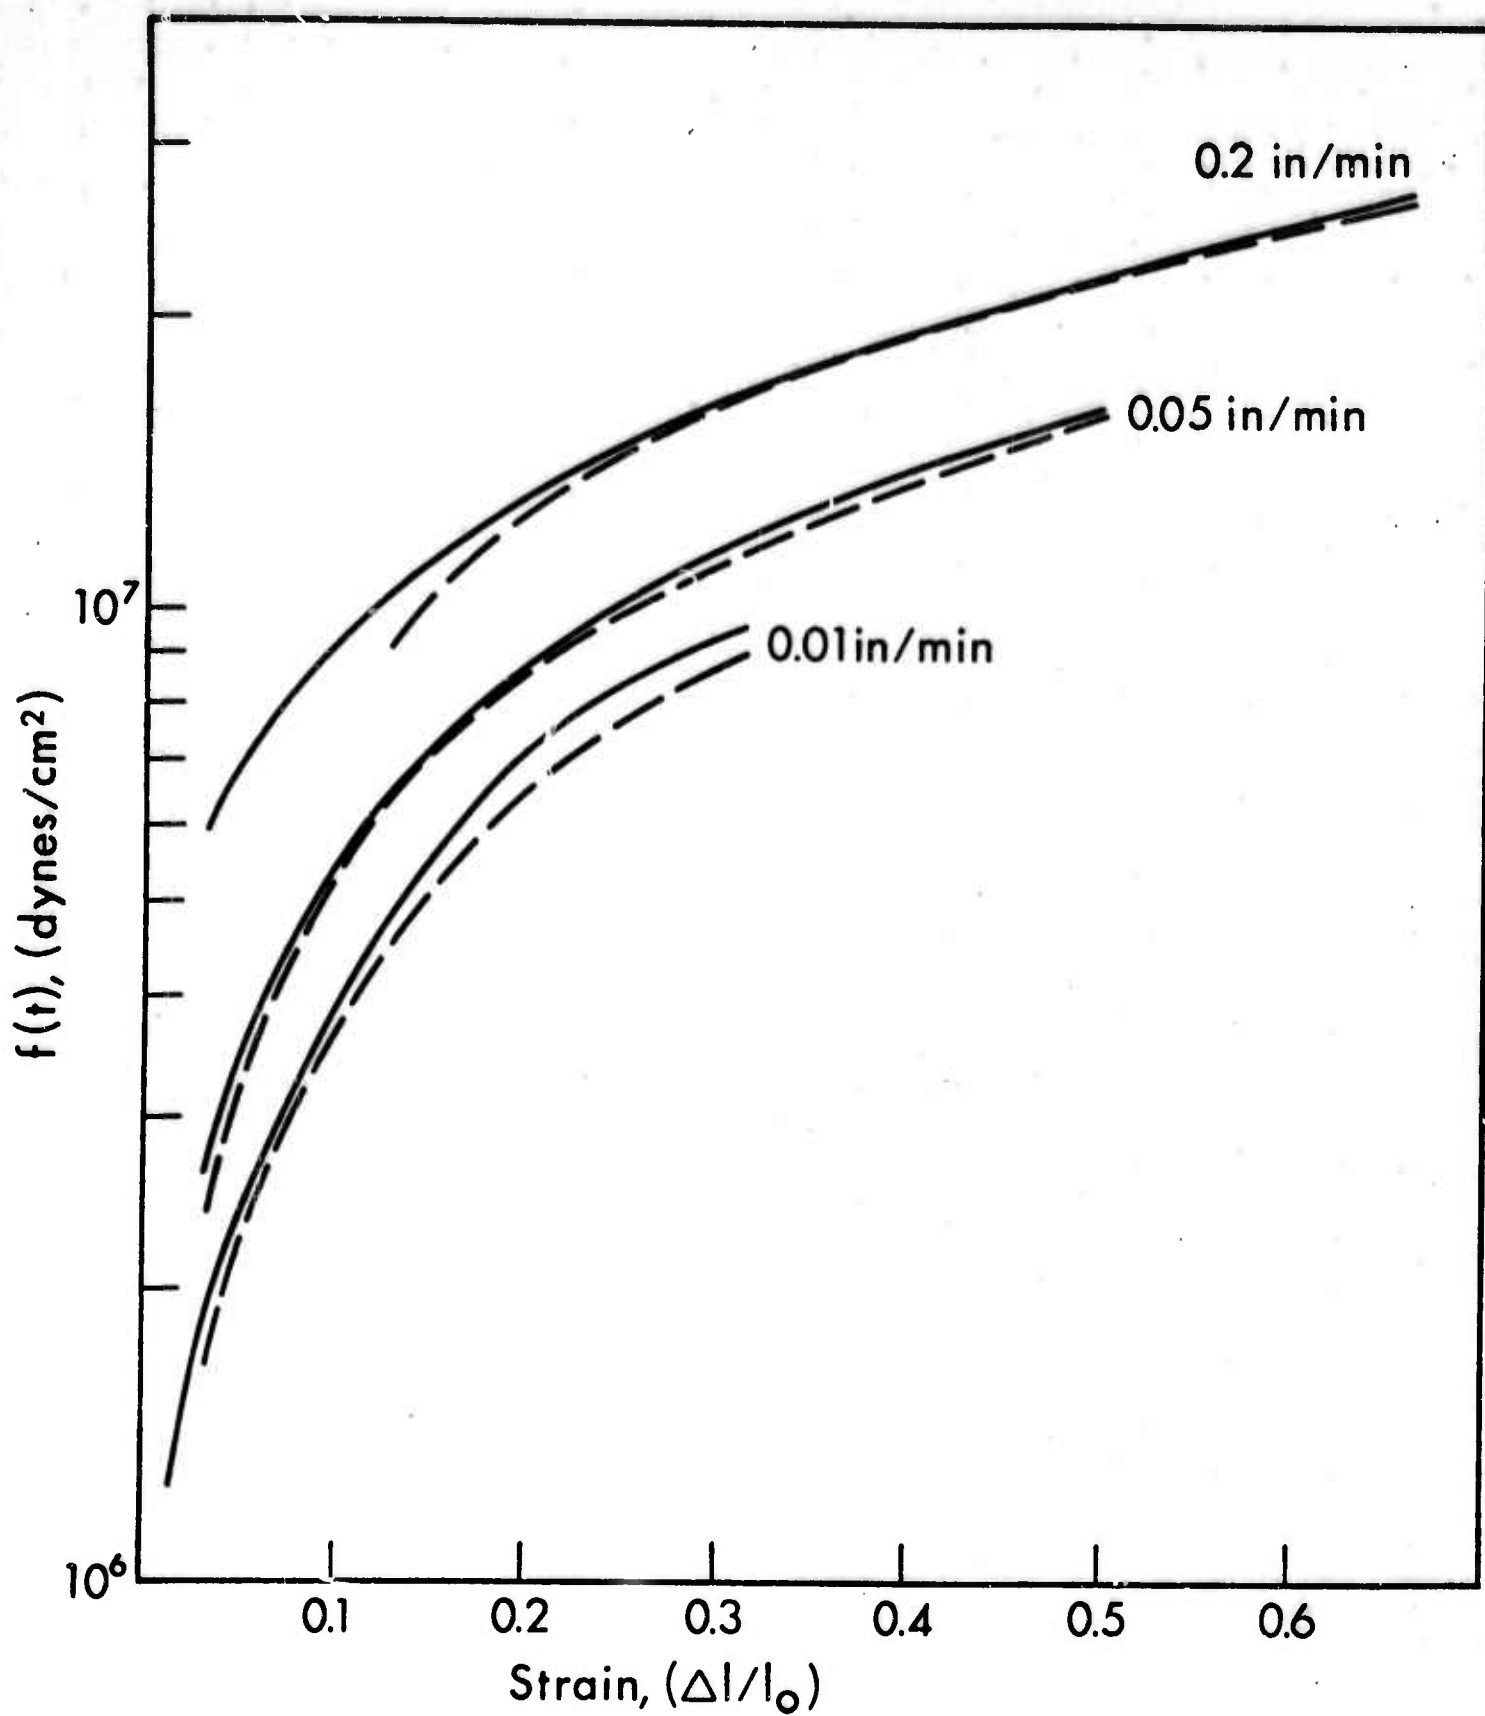

POLYSULFONE 187°C

Fig. 2

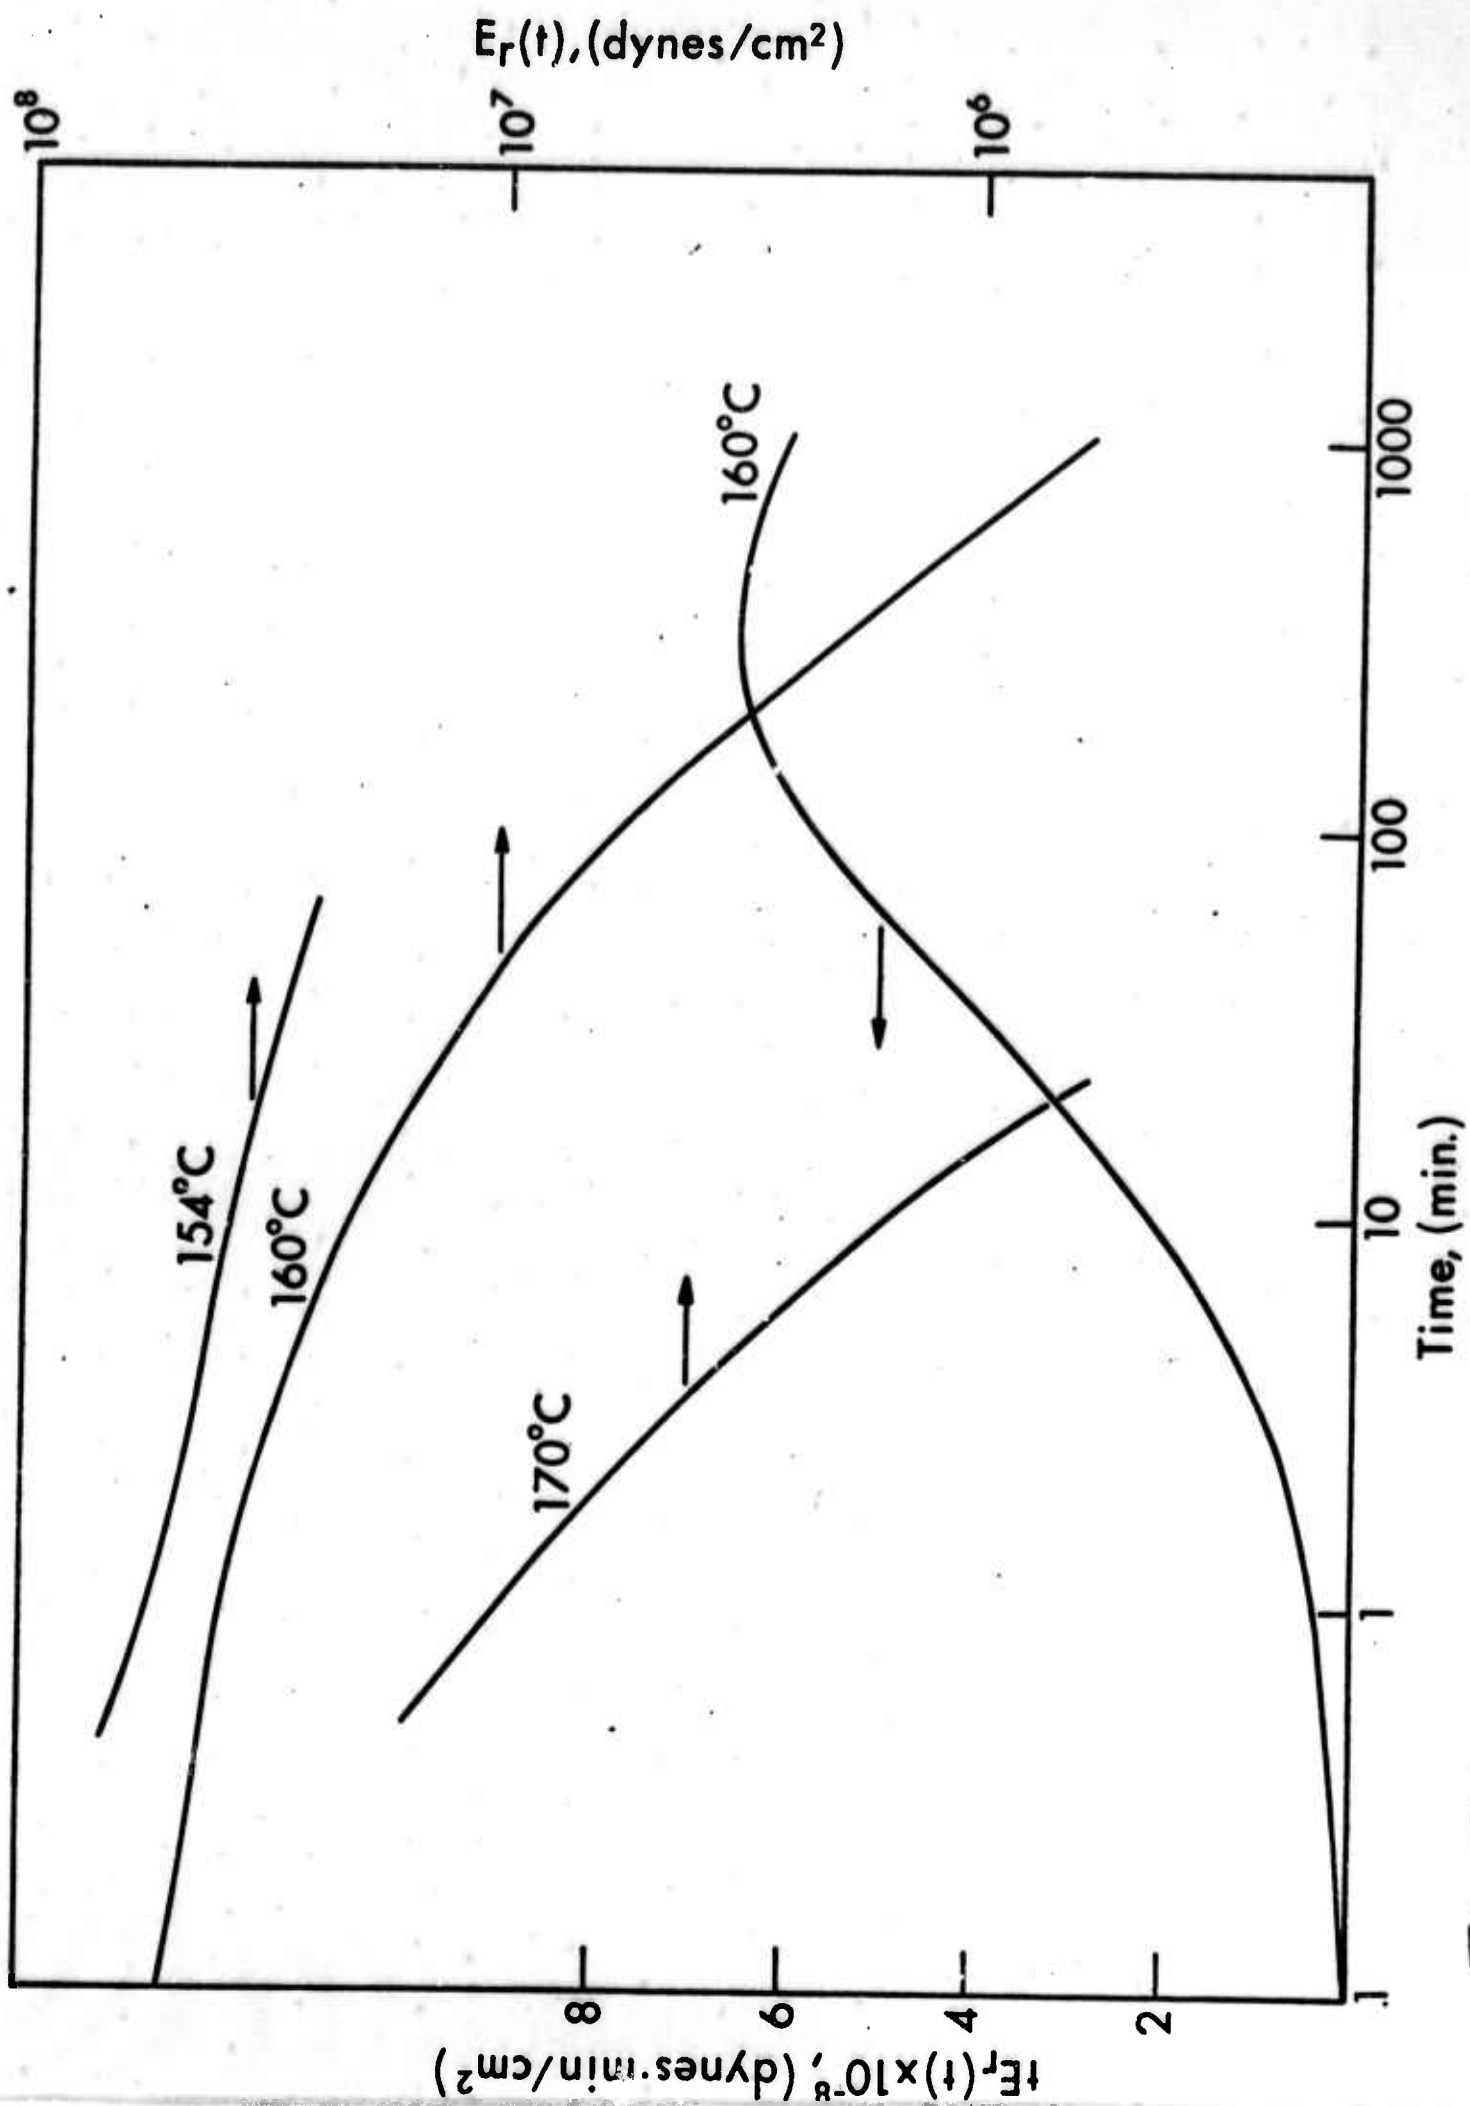


Fig. 3

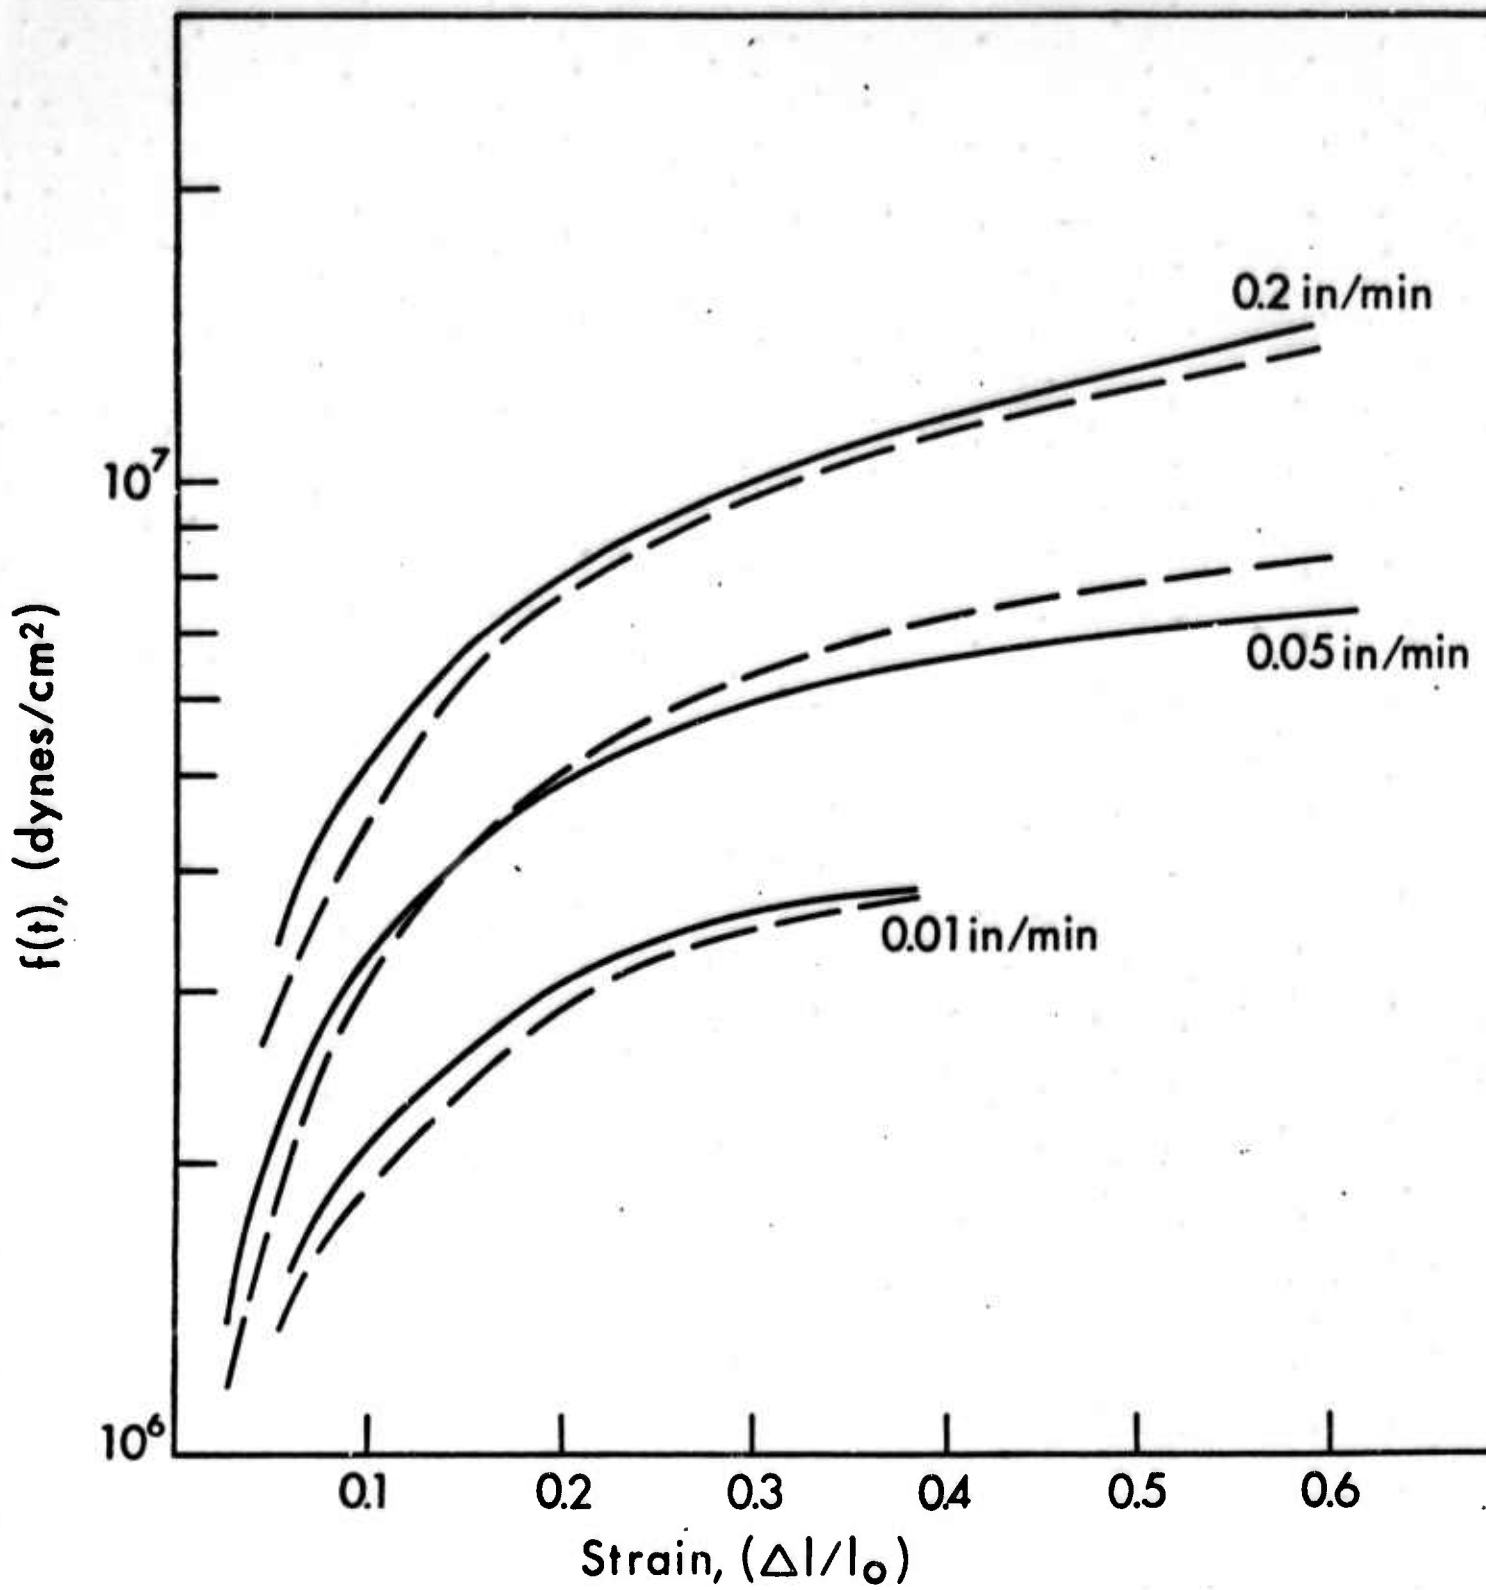


Fig. 4

Security Classification

DOCUMENT CONTROL DATA - R & D

(Security classification of title, body of abstract and indexing annotation must be entered when the overall report is classified)

1. ORIGINATING ACTIVITY (Corporate author)

Monsanto Research Corp.

20. REPORT SECURITY CLASSIFICATION

Unclassified

25. GROUP

3. REPORT TITLE

Calculation of Stress - Strain Curves from Relaxation Data in the Rubbery - J.W. Region

4. DESCRIPTIVE NOTES (Type of report and inclusive dates)

5. AUTHOR(S) (First name, middle initial, last name)

M. Narkis, Washington University, St. Louis, Mo.

6. REPORT DATE

September 1970

7a. TOTAL NO. OF PAGES

22

7b. NO. OF REFS

9

8a. CONTRACT OR GRANT NO.

N00014-67-C-0218

b. PROJECT NO.

9a. ORIGINATOR'S REPORT NUMBER(S)

HPC 70-119

c.

9b. OTHER REPORT NO(S) (Any other numbers that may be assigned this report)

d.

10. DISTRIBUTION STATEMENT

This document is subject of special export controls and each transmittal to foreign governments or foreign nationals may be made only with prior approval of the Director of Material Sciences, Office of Naval Research.

11. SUPPLEMENTARY NOTES

12. SPONSORING MILITARY ACTIVITY

Office of Naval Research
Washington, D. C. 20360

13. ABSTRACT

→ Stress relaxation curves for polysulfone and Lexan polycarbonate are only time dependent at a constant temperature if strain is defined as $\epsilon_H = \ln(l/l_0)$ and the "true" cross-sectional area $A = A_0(1+\epsilon)$ is used. The strain independent stress relaxation curves can be used to calculate stress-strain curves at different rates of strain according to the linear viscoelastic theory. The agreement between experimental and calculated stress-strain curves is good at least up to about 60% strain in the range of 0.01 to 0.2 in/min rate of extension, if an average rate of strain defined by $\dot{\epsilon}_H = 1/t \ln(l/l_0)$ is used.

$$\epsilon_H(t) = \ln(l/l_0)$$

epsilon

DD FORM 1473

1 NOV 65

(PAGE 1)

S/N 0101-807-6801

Security Classification

14. KEY WORDS	LINK A		LINK B		LINK C	
	ROLE	WT	ROLE	WT	ROLE	WT
stress relaxation polysulfone polycarbonate linear viscoelasticity Maxwell-Wiechert body						